

Data sheet

Densit® WearCast 2000

- Chemically bonded Corundum-Ceramic

Densit® WearCast 2000 wear resistant linings provide superior protection against heavy erosive wear at temperatures up to 400°C (750°F).

Consumption at 25 mm

Densit® WearCast 2000	73 kg/m ²
Steel fibres *)	3.3 kg/m ²
Densit® Anchoring mesh	1 m ² /m ²
Densit® Curing Compound	0.25 l/m ²

Consumption at 40 mm

Densit® WearCast 2000	117 kg/m ²
Steel fibres *)	5.3 kg/m ²
Densit® Anchoring mesh	1 m ² /m ²
Densit® Curing Compound	0.25 l/m ²

*) See the data sheet for steel fibres


DENSIT® WEARCAST 2000

- Install mesh
- Install or build mould
- Mix dry compound with water and fibres
- Add water and mix for 6 minutes
- Add appropriate steel fibres*) and mix another 3 minutes
- Pour mix into mould under vibration
- Remove mould after adequate curing time

The bags must be stored on a dry stock to maintain the good properties of the compound.
A paddle mixer must be used for mixing the compound. A significant change in consistency of the material (from dry to plastic) must be observed within 3 minutes from addition of water. Avoid Densit® compound to make contact with aluminium or galvanised steel. Densit® WearCast 2000 should be cast in suitable moulds with adequate reinforcement like steel bars and/or standard expanded metal mesh.

Densit® WearCast 2000 is a castable one-component ready-mix delivered in 25 kg bags.

Technical data

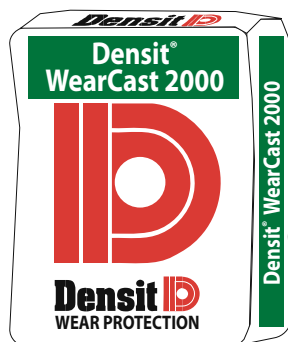

The figures given are typical values.

Please contact ITW Densit or the nearest distributor for further information.

PROPERTIES		Standard	Densit® WearCast 2000
Density	kg/m ³ (lb/ft ³)	EN 1015-6	2950 (184)
Compressive strength	MPa	EN 12190	170
Flexural strength	MPa	EN 196-1	23
Dynamic E-modul	MPa	EN	70-80 10 ³
Casting shrinkage	vol. %		0.2
Thermal conductivity	w/m°C		1.5
Coeff. of thermal expansion	1/°C (1/°F)	EN 1770	10x10 ⁻⁶ (5.6x10 ⁻⁶)
Heat capacity	KJ/kg°C		0.9-1.0
Max. service temperature	°C (°F)		400 (750)
Abrasion resistance	cm ³ /50cm ²	DIN 52108	0.5-1.0
Erosive resistance	min/cm ³		140
Chemical composition	% CaO % SiO ₂ % Al ₂ O ₃ + TiO ₂ % Fe ₂ O ₃ % Cr ⁶⁺	EN 196-10	18 25 55 <0.2 <0.0002
Bag size	kg		25
Pallet size	kg		1250

ITW Densit®

ITW Densit ApS · Tel.: +45 9816 7011 · Fax: +45 8818 4979 · mail@densit.com · www.densit.com
German office:

ITW Densit ApS · Fritz-Peters-Str. 40 · D-47447 Moers · Tel.: +49 2841 88237-0 · Fax: +49 2841 88237-10